

Abstract

This article presents a comprehensive review of sustainable and eco-friendly construction materials for livestock housing systems, with emphasis on their efficacy in ameliorating thermal stress and enhancing animal welfare. Environmental changes directly influence livestock productivity and reproduction, with climate-induced alterations reducing production efficiency by approximately 58.3% and reproductive performance by 63.3%. This article examines diverse eco-friendly materials including bamboo, paddy straw, hempcrete, geopolymers, and agricultural by-products (wool and goat hair), along with modifications to roof, bedding, and floor systems. Comparative analysis reveals that materials such as sheep wool provide thermal conductivity of 0.044 W/m-K and exceptional moisture absorption capacity (25-30% of body weight), while bamboo demonstrates compressive strength of 40 MPa and superior flexibility. Case studies from research institutions demonstrate that green roofing systems and paddy straw insulation reduce internal temperatures by 9.81°C and improve milk yield by 114 kg per cow during standard lactation. The utilization of locally available agricultural and livestock by-products offers economically viable solutions for sustainable and climate-adaptive livestock housing, significantly reducing construction costs without compromising performance or animal welfare.

Introduction

Definition and Significance of Eco-Friendly Materials

Eco-friendly construction represents a behavioral and organizational approach that minimizes environmental harm through the selection and implementation of materials and practices that maintain ecological balance while meeting functional requirements. The concept extends beyond mere material choice to encompass the entire lifecycle of construction—from sourcing and production to application and eventual disposal. In the context of livestock housing, eco-friendly materials serve dual purposes: environmental stewardship and improvement of animal welfare through enhanced microclimate management.

Global Climate Crisis and Livestock Production

The trajectory of global temperature increase presents an unprecedented challenge to livestock production systems worldwide. International Panel on Climate Change projections indicate that earth's surface air temperature will rise by 1.1 to 2.9°C under low-scenario conditions and 2.4 to 6.4°C under high-scenario conditions during the 21st century. This warming trend directly impacts livestock productivity through altered microenvironments, disrupted feeding patterns, and compromised physiological functioning of animals.

The Imperative for Sustainable Housing Solutions

In India and other tropical regions, livestock production faces unprecedented

pressure from heat stress, particularly during summer months. The escalating global temperatures necessitate a paradigm shift in housing design from conventional materials toward sustainable alternatives that provide superior thermal regulation, cost-effectiveness, and minimal environmental footprint. The adoption of eco-friendly construction materials represents not merely an ethical imperative but an economic necessity for sustainable agricultural development.

Environmental Impact on Livestock Production and Reproduction

Heat Stress Effects on Productivity

Climatic variations exert profound effects on livestock performance metrics. Research demonstrates that alterations in climatic conditions directly reduce production levels by 58.3% and reproductive performance by 63.3%. Animals experiencing heat stress demonstrate significantly elevated maintenance energy requirements, with estimates suggesting increases of 20-30% during thermal stress periods. This elevated energy consumption diverts metabolic resources away from productive functions such as milk production and growth.

Heat stress induces electrolyte imbalances through increased loss of ions, particularly sodium and potassium, which are critical for maintaining osmotic balance and cellular function. Additionally, heat stress constitutes a major contributing factor to declining fertility in lactating dairy cows, with conception rates and pregnancy rates declining by 20-30% in hot climatic conditions.

Cold Stress Implications

Contrary to popular misconception that coldness merely reduces milk yield, cold stress presents equally severe challenges to livestock welfare and productivity. For every 1°C decrease in ambient temperature, beef cattle require approximately 2.89 kJ/kg additional maintenance

energy. Cold environments induce alterations in hepatic thermogenic gene expression, as documented in Mongolian sheep studies. Furthermore, digestive function becomes inhibited under cold stress, rendering increased dry matter intake inadequate for meeting elevated heat production requirements, ultimately leading to declining growth performance. Cold stress also measurably reduces standing and walking time, indicating behavioral alterations and potential welfare concerns.

Characteristics and Comparative Analysis of Eco-Friendly Building Materials

Traditional and Emerging Eco-Friendly Materials

Multiple construction materials exhibit environmental sustainability characteristics while providing functional benefits for livestock housing applications. Understanding their respective merits and limitations enables informed material selection for specific environmental conditions and economic constraints.

Earthen and Clay-Based Materials: Earthen construction employs natural soil components combined with organic binders, offering comfort and low-cost advantages. However, earthen structures demonstrate poor hygiene characteristics and become problematic during precipitation events, requiring frequent maintenance and replacement.

Cellulose Materials: Derived from recycled paper waste, cellulose provides excellent thermal and water permeability characteristics. Limitations include reduced load-bearing capacity, restricting applications primarily to insulation and filler functions rather than structural elements. Market pricing typically ranges from 50-60 INR per kilogram.

Wood: High structural strength and flexibility render wood suitable for multiple housing applications, with tensile qualities providing rigidity under load. Primary disadvantages include inherent flammability, vulnerability to rodent damage, and poor water permeability. Construction costs range from 350-550 INR per square foot.

Straw and Thatch Materials: Agricultural residues such as straw provide economical and readily accessible resources with superior thermal insulation properties. Water infiltration leading to soggy conditions, poor hygiene, and rapid degradation necessitate frequent replacement, with costs ranging from 8-15 INR per kilogram for loose straw or 50-80 INR per square foot for bale panels.

Sheep Wool: Natural wool fibers demonstrate excellent thermal insulation characteristics and inherent flame resistance. Primary limitations involve sensitivity to prolonged moisture exposure and the relatively high cost of processing, ranging from 40-60 INR per kilogram for raw wool.

Bamboo: This rapidly renewable resource exhibits exceptional flexibility and extraordinary tensile strength, enabling utilization for flooring, roofing, and structural applications. Bamboo demonstrates compressive strength of 40 MPa and tensile strength of 6 MPa, with thermal conductivity of 0.060 W/mK. Market pricing typically ranges from \$120/m³. Primary limitations include pest sensitivity and requirement for chemical treatment to ensure durability.

Hempcrete: Composed of hemp fibers bound with lime binders, hempcrete provides lightweight, insulating, and non-toxic properties with exceptional moisture regulation. Thermal conductivity measures 0.095 W/mK. Significant limitations include material expense and limited commercial availability, with costs approximately \$140/m³.

Geopolymers: Alkali-activated materials produced from industrial waste streams demonstrate high compressive strength (42.1 MPa) and exceptional tensile strength (25.1 MPa), with thermal conductivity of 0.080 W/mK. Production results in carbon dioxide and greenhouse gas emissions up to 10 times lower than Portland cement-based materials, with electricity consumption reduced by 4-8 times. Challenges include limited field acceptance, regional variations in raw material availability, and elevated initial costs (\$79.22/m³).

Thermal and Physical Properties Comparison

Comparative analysis of nine natural building material samples reveals crucial performance variations. Density measurements ranged from 15 kg/m³ (sheep wool) to 2150 kg/m³ (earthen plaster), with thermal conductivity spanning from 0.041 W/m-K (calcium silicate board, hemp insulation, wood fiber board) to 0.79 W/m-K (earth plaster with straw). Water vapor permeability demonstrated inverse correlation with thermal conductivity, with sheep wool and hemp insulation maintaining 3 units of permeability.

Materials with density exceeding 100 kg/m³ function as construction elements for structural applications and plaster systems, while materials below 100 kg/m³ serve primarily as insulation products. Sheep wool emerged as the superior insulation material with thermal conductivity of 0.044 W/m-K, comparable to modern synthetic alternatives while offering natural, renewable properties.

Scope of Housing Modifications for Livestock

Comprehensive animal housing improvements encompass systematic modifications across multiple structural components: roof systems, floor configurations, bedding materials, and wall panel installations. Each modification targets specific microclimate parameters—temperature, relative humidity, thermal humidity index, and radiant heat load—

to create optimal conditions for animal comfort and productivity.

Case Studies Demonstrating Practical Applications

Green Roofing for Heat Stress Amelioration

A comparative study examining green roofing systems in crossbred calves demonstrated significant performance improvements over conventional asbestos roofing. Animals housed under green roof systems (earth-based roofing covered with seasonal vegetable plants including bottle gourd, pumpkin, and ridge gourd) achieved average body weights of 86.33 ± 6.25 kg, compared to 77.08 ± 6.25 kg for calves under conventional asbestos roofing, representing an 11.9% improvement in growth performance.

Microclimate evaluation revealed temperature differences of up to 1.34°C between asbestos and green roof systems, with green roofing maintaining internal temperatures at approximately 29.56°C compared to asbestos-roofed structures at 30.04°C . Thermal humidity index (THI) values decreased from 84.67 ± 0.24 in asbestos-roofed structures to 83.61 ± 0.20 in thatched ceiling systems with false insulation, representing meaningful reductions in thermal stress indicators.

Comparative Analysis of Roofing Materials During Rainy Season

Research conducted at IVRI Bareilly evaluated three roofing materials—thatch, agro-net shade, and asbestos—during monsoon periods from June to September. Temperature measurements taken both on roof external surfaces and internal ceiling positions revealed dramatic performance variations.

During the initial rainy season month at 9:30 AM, external roof temperatures measured $61.90 \pm 8.78^\circ\text{C}$ for thatch, $34.08 \pm 2.70^\circ\text{C}$ for agro-net, and $50.56 \pm 6.08^\circ\text{C}$ for asbestos. Internal ceiling temperatures demonstrated more

moderate variations: thatch at $32.62 \pm 3.25^\circ\text{C}$, agro-net at $25.82 \pm 0.91^\circ\text{C}$, and asbestos at $37.54 \pm 5.03^\circ\text{C}$.

Thermal humidity index analysis consistently favored thatch and agro-net materials over asbestos throughout the rainy season. Overall THI values measured 76.3 ± 0.32 (thatch), 74.92 ± 0.36 (agro-net), and 77.0 ± 0.29 (asbestos), with agro-net demonstrating superior performance in maintaining favorable microenvironmental conditions.

Paddy Straw Insulation for Seasonal Temperature Regulation

Research at NDRI Kalyani implemented false ceiling systems using paddy straw insulation beneath asbestos roofing on 20 lactating Jersey crossbred cows. This economical modification involved placing 3-4 inch thick paddy straw pads supported by bamboo splits over structural frames. Results demonstrated remarkable thermal benefits throughout distinct seasonal periods.

During rainy season conditions, ceiling temperatures with straw insulation (T1) measured $29.73 \pm 1.84^\circ\text{C}$ in morning observations compared to $38.90 \pm 2.56^\circ\text{C}$ without insulation (T0), representing a temperature differential of 9.81°C . Afternoon measurements showed T1 at $32.05 \pm 1.80^\circ\text{C}$ versus T0 at $40.43 \pm 2.65^\circ\text{C}$, a difference of 8.38°C .

Summer season observations revealed consistent performance, with morning temperatures of $27.41 \pm 2.03^\circ\text{C}$ (T1) versus $36.53 \pm 1.91^\circ\text{C}$ (T0) and afternoon values of $32.33 \pm 2.28^\circ\text{C}$ (T1) versus $37.49 \pm 2.13^\circ\text{C}$ (T0). Winter season data demonstrated that straw insulation-maintained temperatures at $21.26 \pm 2.20^\circ\text{C}$ (T1) versus $24.03 \pm 2.39^\circ\text{C}$ (T0) in morning measurements, and $24.23 \pm 2.35^\circ\text{C}$ (T1) versus $28.03 \pm 2.63^\circ\text{C}$ (T0) in afternoon observations.

Calculated over a standard 300-day lactation period, this thermal management system generated an estimated additional milk yield of 114 kg per cow, demonstrating substantial economic returns from minimal capital investment in agricultural by-products.



Fig : Roofing panel prepared from paddy straw

Flooring Material Preferences in Dairy Goats

Turkish research with 20 polled Saanen goats evaluated behavioral patterns across different flooring materials including straw bedding, rubber, wooden, and slatted surfaces. Goats allocated majority of observation time to inactivity (91.62% of total time regardless of flooring type or season), with activity distribution showing 74.88% lying behavior and 16.73% standing behavior.

Material preference ranking emerged as follows: straw bedding > rubber > wooden > slatted surfaces. Seasonal variations in preference patterns were minimal, suggesting consistent behavioral responses to flooring characteristics. Summer observations occurred at 120 days of lactation with body weight of 54.1 kg, while winter evaluations took place at 90 days of gestation with body weight of 59.3 kg.

Bedding Material Assessment in Lambs

Spanish research examined four bedding materials—sawdust, cellulose, straw, and rice husk—in fattening lambs using comprehensive scoring systems for material characteristics. Straw bedding demonstrated highest dirtiness (score 2.60) and wetness (score 2.80) ratings, with overall score of 1.89, compared to cellulose

and rice husk materials averaging 0.62-1.11 overall scores.

Despite hygiene disadvantages, straw remained economically optimal at €1.00 per 10.7 m² area, compared to €2.35 (rice husk), €2.80 (cellulose), and €13.50 (sawdust). Behavioral observations showed lambs spent 79.07% time lying on straw versus 75.25-77.57% on alternative materials, suggesting behavioral preference despite material cleanliness limitations. Standing time decreased on straw (11.67%) compared to alternative materials (13.27-15.87%), indicating postural comfort advantages of straw bedding.

Bamboo Architecture for Sheep and Goat Shelters

Nigerian research demonstrated sustainable shelter construction utilizing bamboo structural frameworks with raffia palm leaf roofing. Bamboo columns were erected and secured through nail and wire binding, with concrete foundations providing stability and earth flooring providing natural, temperature-regulating surfaces.

Bamboo structures achieved construction costs 30% lower than traditional materials while providing 50% durability improvements and 25% thermal comfort enhancements. Bamboo's inherent properties—exceptional strength, flexibility, and rapid renewability—rendered it suitable for constructing economically viable and durable shelters significantly enhancing animal welfare across multiple parameters.

Wool Fiber Composite Development

Sheep wool is a highly sustainable material offering strong thermal insulation, natural moisture buffering, and zero ozone depletion potential. Its thermal conductivity is comparable to polystyrene, while its breathability helps prevent condensation. Wool fibres can also reinforce concrete, where they slightly reduce compression strength but significantly improve flexural strength—up to

18% at higher dosages. Additionally, wool acts as an efficient carbon-fibre precursor, providing 16–25% yield and about 77% carbon content after chemical treatment and carbonization.

capacity to absorb up to 25-30% of its own weight in moisture while gradually releasing it, contributing to beneficial thermal and humidity regulation in animal housing microenvironments.

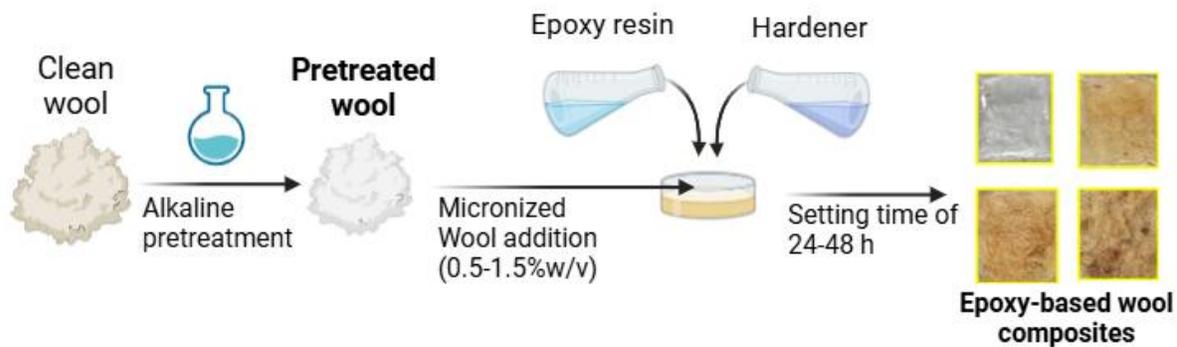


Fig : Epoxy-based sheep wool composites

Research at IVRI Bareilly developed wool-reinforced polymer composites for animal housing applications. Epoxy matrices incorporated wool fiber concentrations ranging from 0% to 1.5% by weight. Compression strength increased from 15.51 MPa (0.5% wool) to 45.77 MPa (1.5% wool) concentration, while thermal conductivity decreased from 3.29 W/m-K (control) to 2.35 W/m-K (1.5% wool), indicating improved insulation characteristics.

For practical housing applications, a 0.01-meter-thickness sheet with 100 m² coverage area could adequately house 50 goats. Economic analysis

Cow Dung Utilization in Construction

Recent advancement research demonstrated cow dung integration in adobe brick formulations. Natural plant fibers present within cow dung composition prevented crack propagation and reinforced material structure, resulting in homogeneous adobe microstructure. Fiber presence enhanced mechanical strength while significantly improving water resistance of bricks, rendering cow dung-stabilized adobe advantageous for wet and tropical climatic applications.



Fig : Cow dung based construction material

revealed composite material costs of approximately Rs. 6440 per cubic meter using 1.5% wool concentration with epoxy binding. Moisture absorption studies demonstrated sheep wool

Bamboo Fiber-Reinforced Agrostone Panels

Research evaluated bamboo fiber replacement of conventional fiberglass in magnesium oxide-based agrostone panels.

Testing revealed optimal performance at 8% fiberglass replacement by bamboo fiber. Bending strength measurements indicated consistent performance across replacement levels (4.49-4.55 MPa), confirming that bamboo fibers adequately substitute conventional glass fibers while reducing material costs and environmental impact.

Chemical analysis of pretreated bamboo (5% sodium hydroxide treatment) showed cellulose content increase from 43.41% to 55.48%, hemicellulose decrease from 23.96% to 19.85%, and lignin reduction from 24.25% to 20.98%, indicating chemical treatment optimization for fiber reinforcement applications.

Goat Hair Fiber Reinforcement

Goat hair fibers demonstrated remarkable properties for cement composite reinforcement: average length of 19 mm with diameter of 0.0003 mm, yielding approximately 7,445,845 fibers per kilogram. Material density ranged from 1.5-1.6 g/cm³ with tensile strength ranging 287-800 MPa. Chemical incorporation in lightweight mortar and cement composites increased flexural strength by 21.8% and compressive strength by 21.5% at 0.5% water-to-cement ratios.



Fig : Goat hair fibres

Future Prospects for Sustainable Livestock Housing

Enhanced Green Roofing Systems

Development of green roofing systems incorporating carefully selected vegetation

providing triple benefits—thermal regulation, fodder production, and income generation—should receive priority implementation. Roofing designs should integrate appropriate flora species adapted to regional climate conditions while providing structural stability and animal safety.

Straw-Rubber Bedding Integration

Conventional straw bedding combined with underlying rubber mat foundations can provide superior comfort through soft, cushioned surfaces reducing joint stress while maintaining drying capability underneath. This layered approach preserves hygiene benefits of rubber systems while providing behavioral preference advantages of straw materials.

Holistic Passive Cooling Approach

Integration of multiple passive cooling strategies—including modified roof materials, side wall configurations, ventilation openings, and appropriate bedding materials—can create comprehensive microclimate management systems achieving thermal comfort without active energy consumption or mechanical systems.

Economic Analysis and Farmer Implementation

Economic analysis of wool-based insulation development indicates potential for adding value to locally available materials, boosting regional manufacturing capabilities, and fostering sustainable agricultural development. Regional manufacturing initiatives can create employment opportunities while supporting livestock productivity improvements.

Zero-Energy Cool Construction

Implementation of zero-energy cool construction (ZECC) principles incorporating locally available materials with passive cooling designs can establish low-cost, maintenance-efficient, energy-efficient, and welfare-based animal housing systems suitable for resource-limited farming communities.

Conclusions

This comprehensive review demonstrates conclusively that eco-friendly construction materials effectively enhance livestock comfort by systematically reducing both heat and cold stress through superior thermal management properties. Specific conclusions include:

Material Efficacy: Eco-friendly materials including bamboo, paddy straw, hempcrete, geopolymers, and agricultural by-products provide thermal conductivity values (0.041-0.095 W/m-K for insulation materials) comparable to or superior to conventional construction materials while offering sustainability advantages.

Performance Improvements: Roof and bedding modifications utilizing eco-friendly materials demonstrably improve microclimate parameters, animal productivity metrics, and overall welfare compared to conventional asbestos or concrete housing systems. Case study evidence documents milk production increases of 114 kg per cow during standard lactation periods and growth improvements of 11.9% in calves.

Economic Viability: Low-cost and sustainable resource utilization provides substantial economic benefits, reducing both construction and maintenance costs without compromising performance or animal welfare. Bamboo structures cost 30% less than conventional materials while improving durability 50% and thermal comfort 25%.

Sustainability Integration: Utilization of locally available agricultural and livestock by-products offers practical solutions for sustainable and climate-adaptive livestock housing systems. These materials reduce environmental impact through waste utilization, lower carbon footprint during production, and decreased transportation requirements.

Welfare Enhancement: Systematic housing modifications incorporating eco-friendly materials create optimal microenvironmental conditions supporting animal welfare objectives including reduced thermal stress, improved comfort, enhanced productivity, and behavioral preference alignment with natural livestock behaviors.

The convergence of environmental necessity, economic advantage, and animal welfare improvement renders eco-friendly livestock housing construction not merely an optional improvement but an essential component of sustainable and resilient agricultural systems. Implementation of these materials and practices represents a transformative approach to livestock production capable of addressing contemporary challenges of climate change, resource scarcity, and sustainability demands.

References :

- Asish Debbarama*, Dilip Kumar Mandal and Ajoy Das 2022 Amelioration Of Heat Stress in Dairy Cows Through Shelter Management- An Overview *International Journal of Livestock Research, Vol. 12 (10)* Oct'2022
- Siyuan Wang, Qi Li, Jianhao Peng and Huaxin Niu* 2023 Effect of Long-Term Cold Stress on Growth Performance, Behaviour, Physiological Parameters, and Energy Metabolism in Growing Beef Cattle *Animals*,2023
- A Nowotna , B Pietruszka and P Lisowski 2024 Eco friendly building materials *IOP Publishing*
- Yonatan Ayele Abera 2024 Sustainable building materials: A comprehensive study on eco-friendly alternatives for construction *Composite and advanced materials Vol 33(1-17)*

- Upendra Singh Narwaria, Mukesh Singh and Kuldeep Kumar Verma 2020 Effect of false ceiling on microclimatic variables of crossbred cattle during rainy season *Indian J.Anim.Prod.Mgmt. Vol. 35(3-4)*
- Reena Kamal, Triveni Dutt, B.H.M. Patel, R.P. Ram, Probhakar Biswas, P.K. Bharti and Sandeep Kaswan 2013 Effect of roofing materials on micro-climate in loose house for animals during rainy season *Vet World 6(8):482-485*
- D K Mandal, Dharma Sahu, A Mandal, A Chatterjee, C Bhakat, Saroj Rai, M Karunakaran and T K Dutta 2018 Alteration of micro-environment of animal shed through roof insulation by paddy straw – its seasonal efficacy and physiological impacts on Jersey crossbred cows *Indian J Dairy Sci 71(5):483-490*
- Cemil Tolu*, Turker Savas 2019 Dairy goat usage of flooring types varied by material, slope and slat width *Applied Animal Behaviour Science 215(2019)37-44*
- D.L.Teixeria, M.Villarroel, G.A.Maria 2014 Assesment of different organic bedding materials for fattening lamb *Small Ruminant Research 119(2014)22-27*
- Odetoeye Sunday Adeola, Shuaibu Nuru Mamman, Ogwuche Henry Audu, and Osunkunle Abdulmageed Abiodun 2024 Design and construction of sheep and goat shelter using Bamboo Architecture in Bauchi *African Journal of Environmental Sciences & Renewable Energy*
- Orsolya Dénes, Iacob Florea, Daniela Lucea Manea 2019 Utilization of sheep wool as a building material *Procedia Manufacturing Vol 32 (236-241)*
- Laveena Sambhwani, Ayon Tarafdar, Hari Om Pandey 2025 Upcycling of wool for the development of polymer composites for animal housing applications
- Najmeh Hassas, Farzam Omid Moaf, Matzena Kurpinska, Teresa Bardzinska-Bonenberg, Justyna Borucka, Hakim S. Abdelgader, Rohan Soman and Mikolaj Miskiewicz 2025 The impact of goat hair as a natural animal fiber on properties of the lightweight cement composite *Scientific reports*
- Sanchit Gupta and Sandeep Chaudhary 2023 Recent advancements utilizing cow dung
- Bahiru Bewket Mitikie, Simachew Birlie Chekele and Walied A Elsaigh 2025 Bi-product utilization of eco-friendly agro stone panels: bamboo fiber as a cost effective fiberglass substitute in low cost housing *Material Research Express 12*
- Febin Stephan 2022 Development and Evaluation of An Energy Efficient Cool Housing System To Alleviate Heat Stress in Murrah Buffalo Calves During Summer Season